

## **Influence of Blend Ratio on Thermal Properties of Bamboo/Cotton Blended Woven Fabrics**

Prakash Chidambaram<sup>1\*</sup> and Ramakrishnan Govindan<sup>2</sup>

<sup>1</sup>*Department of Fashion Technology, Sona College of Technology, Salem, India*

<sup>2</sup>*Department of Fashion Technology, Kumaraguru College of Technology, Coimbatore, India*

*\*Corresponding author. E-mail address: dearcpakash@rediffmail.com*

Received March 28, 2012; Accepted June 11, 2012

### **Abstract**

Thermal comfort characteristics of plain woven fabrics made out of 30<sup>s</sup> Ne<sub>c</sub> cotton in warp and 30<sup>s</sup> Ne<sub>c</sub> 100% bamboo, bamboo/cotton blended yarns in weft have been studied. The fabric characteristics such as air permeability, wicking, thermal resistance, relative water permeability related to comfort characteristics are discussed. The experimental results show that 30<sup>s</sup> Ne<sub>c</sub> cotton in warp and 30<sup>s</sup> Ne<sub>c</sub> bamboo in weft plain woven fabric exhibits higher air permeability when compared to other samples, 30<sup>s</sup> Ne<sub>c</sub> cotton in warp and 30<sup>s</sup> Ne<sub>c</sub> bamboo in weft plain woven fabric shows very low thermal resistance and higher wicking rate than other samples. Relative water permeability value of 30<sup>s</sup> Ne<sub>c</sub> cotton in warp and 30<sup>s</sup> Ne<sub>c</sub> bamboo in weft fabric is higher and that of 30<sup>s</sup> Ne<sub>c</sub> cotton both in warp and weft fabrics are lower when compared to other samples.

**Key Words:** Thermal properties; Air-permeability; Water-vapour permeability; Thermal resistance; Wickability

### **Introduction**

Life standard is nowadays getting higher. The demands of people in all areas are increasing, as well as the requirements regarding new textile materials with new or improved properties which are important for the required higher comfort or industrial use.

Comfort, which defined as states in which there are no driving impulses to correct the environment by the behaviour (Li, 2001). Clothing comfort is closely related to thermal comfort (Watkins et al., 1981; Pac et al., 2001). The body produces lots of heat energy and the body temperature increases. To reduce the high temperature, the body perspires a lot in liquid and vapour form. While this perspiration

is transmitted to atmosphere, the body temperature reduces and then the body feels cool. So the garments should allow the perspiration to pass through, otherwise it will result in discomfort.

Bamboo is an important forest biomass resource. Bamboo textiles have many fantastic properties when used as textile materials such as high tenacity, excellent thermal conductivity, resistant to bacteria, and high water and perspiration adsorption. Yarns of bamboo fibre provide the desirable properties of high absorbency, anti-microbial and soft feel in textiles and made ups. Currently, regenerated bamboo fibres are used in apparels including undergarments, sports textiles, t-shirts and socks. They are also suitable for

hygienic products and sanitary materials such as sanitary napkins, absorbing pads, masks, bandages and surgical gowns (Saravanan et al., 2007; Prakash et al., 2011).

Blending of different fibres is a very common practice in the spinning industries. Blending different types of fibres is a widely practiced means of enhancing the performance and the aesthetic qualities of a fabric. Bamboo blended with cotton is usually 50/50 combinations (Abhijit Majumdar et al., 2010).

Okubo et al. (2005) studied the mechanical properties of bamboo fibres and concluded that the strength of bamboo fibres was equivalent to that of glass fibres. Grineviciute et al. (2007) revealed that hand properties of bamboo fibre better than cotton fabrics. Gun et al. (2008) reported that fabrics made from 50/50 bamboo/ cotton yarns had a similar appearance as compared with those made from 50/50 viscose/cotton and 50/50 modal/cotton. They concluded that the weight, thickness and air permeability was independent of the fibre type. Kawahito (2008) indicated that cotton fabrics had a higher tenacity, greater thickness under a heavier load, faster water absorption and better drying properties than bamboo fabrics.

Filiz Sekerden (2011) studied that the effect of the yarn and weave types on the physical and mechanical properties of the bamboo blended fabrics were examined. He found that the weave type affected the physical and mechanical properties of the fabric more than the fibre mix and type in the weft yarn.

Many researchers have conducted studies to evaluate and analyse the thermal comfort of woven fabrics (Senthilkumar et al., 2010; Tyagi

et al., 2011). The work was aimed to investigate the influence of the bamboo content and compare the thermal comfort parameters of woven fabrics made from 100% cotton yarn, 100% bamboo and bamboo/cotton blended yarns. In this study testing air, moisture and thermal transfer properties such as air permeability, relative vapour permeability, thermal resistance and wickability of plain weave fabrics and studying their comfort characteristics.

### Materials and Methods

In this study, 100% bamboo, 70/30 bamboo/cotton, 50/50 bamboo/cotton, 30/70 bamboo/cotton and 100% cotton yarns were procured from pallava spinning mills (p) ltd, India. It was ensured that all of the yarns produced had the same mean linear density of  $30^s$  Ne<sub>c</sub>. The properties of fibre and yarns were given in Table 1 and 2. In this study, plain woven fabrics were chosen and these fabrics were washed thoroughly with hot and cold water, and given scouring treatment using appropriate recipe. The geometrical properties of woven fabrics are given in Table 3. The test parameters related to thermal and moisture related comfort characteristics are given in Table 4. Weaving process was performed using unsized warp, bamboo fibre was inserted only in the weft system.

**Table 1** Properties of the fibres

Fibre properties	Bamboo	Cotton
Fibre length, mm	36	27.27
Fibre fineness, dtex	1.52	1.70
Tenacity, cN/tex	19.87	33.33
Elongation at break, %	21.11	6.1

**Table 2** Characteristics of bamboo-cotton yarns

Blend ratio	100 % Cotton	70:30 % Cotton/ Bamboo	50:50 % Cotton/ Bamboo	30:70 % Cotton/ Bamboo	100% Bamboo
Yarn Diameter mm	0.198	0.185	0.177	0.166	0.150
Twist/meter	937	912.3	1075	869.6	802
Tenacity RKM	10.67	10.32	7.26	7.34	11.00
Tenacity CV %	28.93	21.85	28.53	31.23	21.08
Elongation at break %	3.22	3.79	3.40	3.72	6.77
Elongation at cv%	30.11	15.23	22.01	38.35	31.97
Thin place/km (-50%)	4540	2036	1096	1433	550
Thin place CV%	3.89	11.28	18.81	55.93	25.92
Thick place/km (+50%)	3725	2628	1464	2102	1027
Thick place CV%	2.36	7.39	11.59	35.62	4.71
Neps/km	3942	2862	1713	2083	1358
Neps CV%	2.56	8.57	19.21	20.09	9.66
Single yarn strength(g)	210.1	203.2	143	144.7	216.7

### Testing

The following tests were carried out for the woven fabrics such as fabric mass, fabric thickness, air permeability, relative water permeability, thermal conductivity and thermal resistance. The standard test procedure BS 2471, 1974 was followed for determining the fabric mass of woven fabrics in this study. Shirley thickness gauge was used for the measurement of fabric thickness as per ASTM D1777. The wicking properties were measured by

the technique of vertical wicking test as per TAPCC standard. The Lees disc method was used to measure fabric thickness and thermal resistance; water vapour permeability was measured on a Permetest instrument working on simulated skin principle as recommended in ISO 11092; fabric air permeability was measured according to the TS 391 EN ISO 9237 using Tester FX3300. All the fabric samples are conditioned at standard atmospheric condition  $65\% \pm 2\% \text{ RH}$  and  $27^\circ\text{C} \pm 2^\circ\text{C}$ .

**Table 3** Geometrical property of woven fabrics

Sample	Warp yarn	Weft yarn	Fabric Thickness mm	Ends/inch	Picks/inch	Warp cover factor ( $K_1$ )	Weft cover factor ( $K_2$ )	Fabric cover factor ( $K_c$ )
A	100% cotton	100% Bamboo	0.26	80	72	14.61	11.69	20.89
B		70:30 Bamboo: Cotton	0.28	80	70	14.61	12.05	20.72
C		50:50 Bamboo: Cotton	0.33	80	69	14.61	12.59	20.63
D		30:70 Bamboo: Cotton	0.36	80	66	14.61	12.78	20.37
E		100% Cotton	0.46	80	64	14.61	13.15	20.19

**Table 4** Thermal transfer properties of plain woven fabrics


Sample	Fabric mass, (g/m <sup>2</sup> )	Thermal resistance, (mkm <sup>2</sup> /w x 10 <sup>-3</sup> )	Relative water permeability (%)	Fabric wicking height, (cms)	Air permeability, (cm <sup>3</sup> /cm <sup>2</sup> /sec)
A	197.32	60.38	48.32	14.4	117
B	204.78	71.89	45.11	12.1	106
C	208.66	80.55	43.22	10.4	99
D	214.89	89.35	41.17	9.2	97.9
E	239.98	97.81	40.04	8.1	97

## Results and Discussion


### Air permeability

The air permeability results of the fabrics are shown in Figure 1. The results indicate that air permeability is higher in the sample A, and when the bamboo fibre content drops below 50%, the fibre proportion is not so effective in air permeability. This can be explained in terms of the enhanced rate of air flow as a consequence of the reduced bulk of bamboo-majority yarns. Higher air permeability

value of Sample A compared with samples B, C, D and E could be because of lower fabric cover factor values. Gün et al. (2008) compared fabrics produced from mixes of 50/50 bamboo/cotton, 50/50 viscose/cotton and 50/50 modal/cotton, and reported that air permeability is independent of fibre type. When Figure 1 is examined, it is observed that air permeability decreases when the proportion of bamboo in the mix decreases.

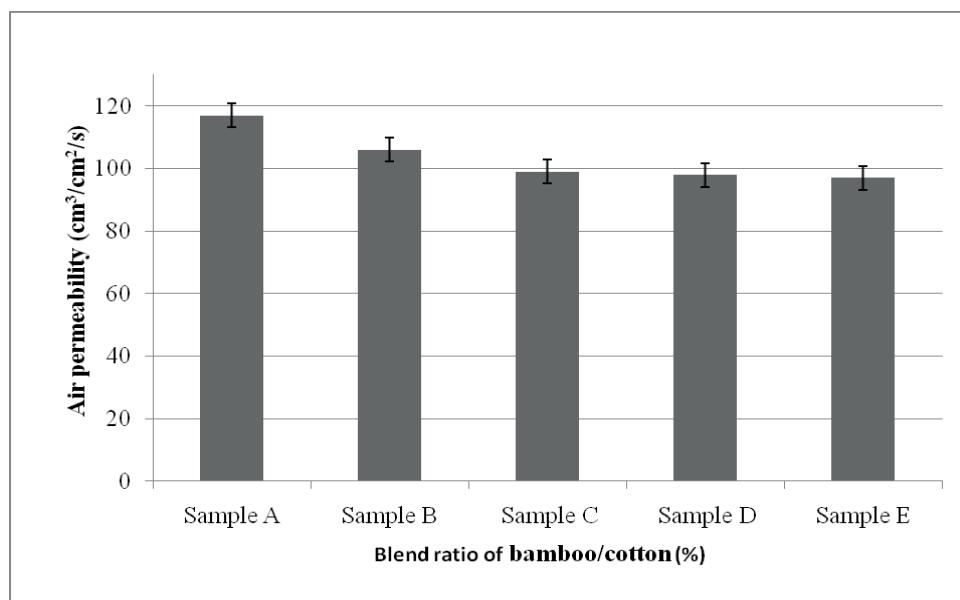**Figure 1** Influence of bamboo/cotton blend ratio on air permeability

### Thermal resistance

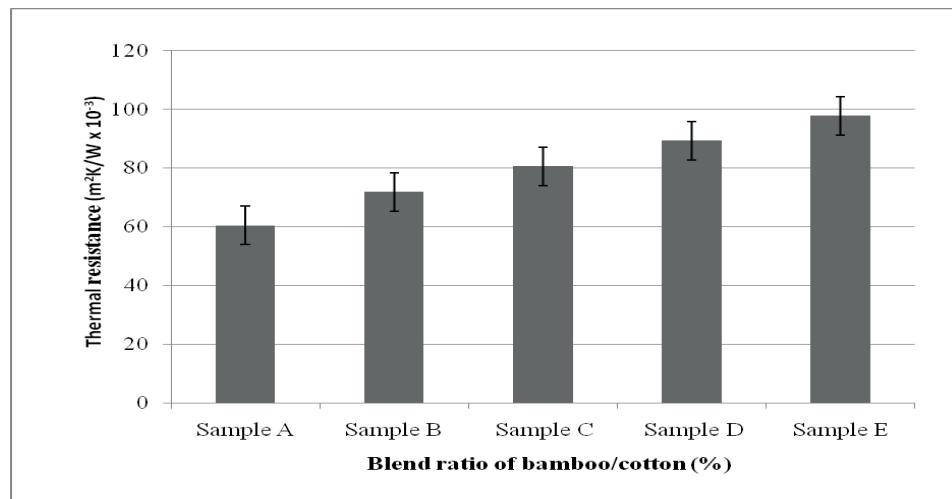


**Figure 2** Influence of bamboo/cotton blend ratio on thermal resistance

The thermal resistance of Sample E fabric exhibits higher value when compared to all other samples. This is due to the higher fabric thickness and higher fabric cover factor. From the results, it is observed that higher thermal resistance values are noticed in the case of thicker fabric. Sample A exhibits lower thermal resistance when compared

to all other samples. This may be due to higher air permeability. An increase in the cotton content in the fibre-mix improves the thermal resistance. The increased cotton content traps the air, making the structure more thermally resistant. Figure 2 also shows that sample E fabrics have significantly higher thermal insulation values than other samples.

### Wicking

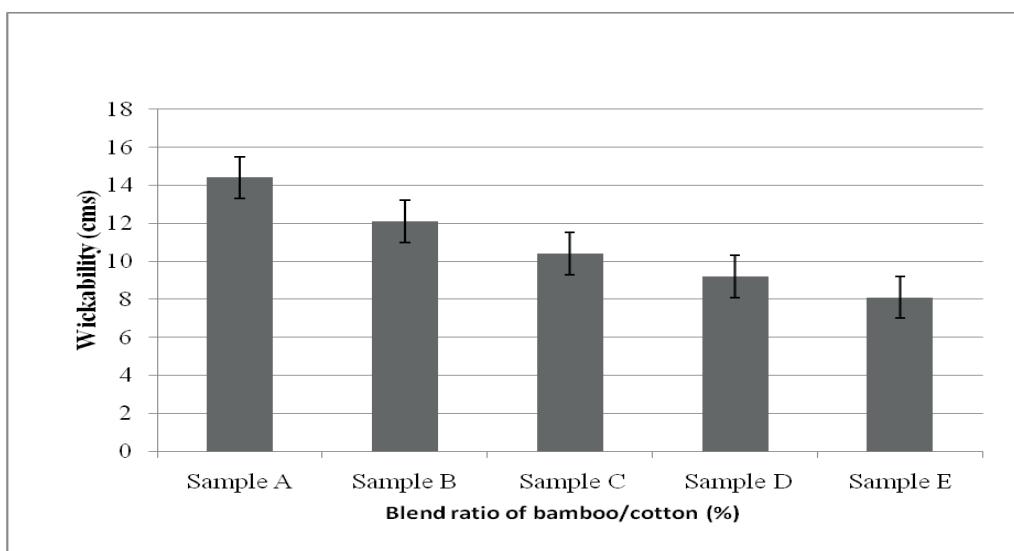


**Figure 3** Influence of bamboo/cotton blend ratio on wickability

Figure 3 shows the results of wickability test. The wicking property of a fabric mainly depends on characteristics of fibre and structure of component yarns and fabric. The experimental results show that Sample A has higher wicking rate when compared to all other samples. Wicking can only occur when fibre assemblies with capillary spaces between them are wetted by a liquid. Sample D exhibits wicking height up to 14.4mm due to better capillary rise and the yarn has soft and smooth feel. As stated, the higher hydrophilicity together with macro channels presented in the bamboo cellulose account for the enhanced wickability of bamboo-majority fabrics

(Erdumlu et al., 2008).

### Water vapour permeability

Figure 4 illustrates the values of water vapour permeability with respect to blend ratio of bamboo. The water vapour permeability is highly dependent on the macro-porous structure of the constituent fibres. The water vapour permeability is considerably higher for the sample A fabrics compared with those for the other samples. Higher moisture regain together with the macro channels presented in bamboo fibre represents no hindrance to moisture transfer in hydrophilic systems (Erdumlu et al., 2008).

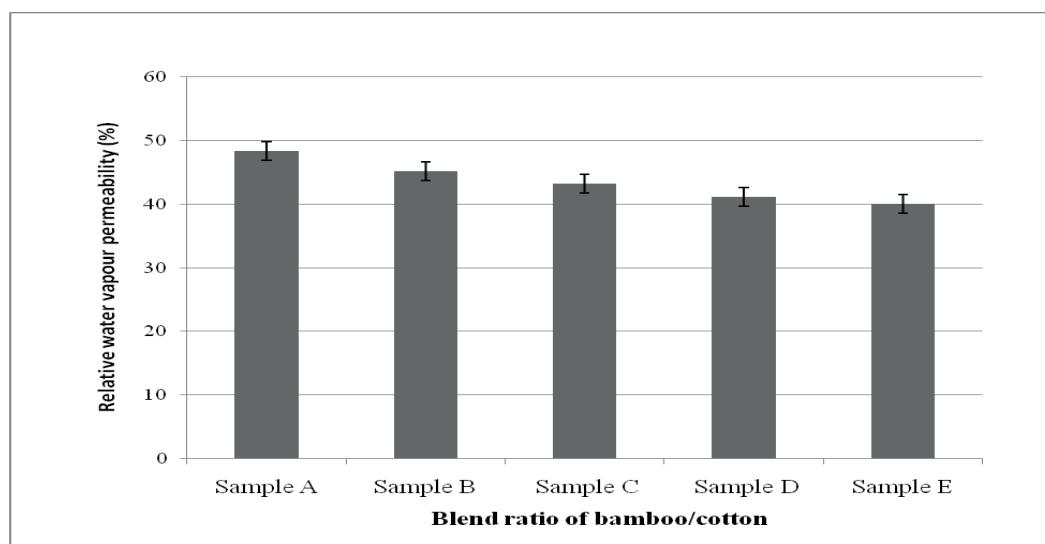

**Figure 4** Influence of bamboo/cotton blend ratio on water vapour permeability

### Conclusion

The thermal comfort parameters of woven fabrics made from 100% cotton yarn, 100% bamboo and bamboo/cotton blended yarns have been analyzed. The fabric comfort characteristics such as air permeability, wicking, water absorption and thermal resistance have been studied. The fabrics produced with higher bamboo content, in general, are substantially more air and water permeable, more absorbent, have lower thermal resistance and yield higher wickability than the equivalent fabrics produced with cotton fabrics.

### Acknowledgements

The authors would like to express their sincere thanks to M. Agalya, T. Mathura, V. Saranya and R. Subathrakala for their assistance in the experimental part, to the management of Sona College of Technology for permission to use the laboratory facilities and lastly to the Textile Research Centre, TIFAC-CORE in Textile Technology and Machinery, of Kumaraguru College of Technology, Coimbatore, India for test all the samples in their advanced manufacturing laboratory.

## References

Erdumlu, N. and Ozipek, B. (2008) Investigation of regenerated bamboo fibre and yarn characteristics. *Fibres & Textiles in Eastern Europe*. 16: 43-47.

Grinevičiūtė, D., Kazakevičiūtė, G., Gutauskas, M., Rimkutė, R., and Abraitienė, A. (2007) Influence of bamboo fibre on fabric hand. *Proceedings of 7th Baltic Polymer Symposium*. 176-80.

Gun, A. D., Unal, C., and Unal, B. T. (2008) Dimensional and physical properties of plain knitted fabrics made from 50/50 bamboo/cotton blended yarns. *Fibres and Polymers*. 9: 588-592.

Kawahito, M. (2008) A comparative study of bamboo shijara fabric and cotton shijara fabric. *Sen-I-Gakkaishi*. 64: 108-112.

Li, Y. (2001) *The Science of clothing comfort*. Textile Progress, Taylor & Francis, Manchester.

Majumdar, A., Mukhopadhyay, S., and Yadav, R. (2010) Thermal properties of knitted fabrics made from cotton and regenerated bamboo cellulosic fibres. *International Journal of Thermal Science*. 40: 2042-2048.

Okubo, K., Fujii, T., and Yamamoto, Y. (2005) Development of bamboo-based polymer composites and their mechanical properties. *Composite Part A-Application system*. 35: 377- 383.

Pac, M. J., Bueno, M. A., and Renner, M. (2001) Warm-cool feeling relative to tribological properties of fabrics. *Textile Research Journal* 71: 806-812.

Prakash, C., Ramakrishnan, G., and Koushik, C. V. (2011) Effect of blend ratio on quality Characteristics of bamboo/cotton blended ring spun yarn. *Fibres and Textile in Eastern Europe* 19: 38-40.

Saravanan, K. and Prakash, C. (2007) Bamboo fibres & their application in textiles. *The Indian Textile Journal*. 117: 33-36.

Sekerden, F. (2011) Investigation on the unevenness, tenacity and elongation properties of bamboo/cotton blended yarns. *Fibres and Textile in Eastern Europe*. 19: 26-29.

Senthilkumar, P., Kantharaj, M., and Vigneswaran, C. (2010) Thermal comfort characteristics of plain woven fabrics. *Journal of Textile Association*. 71: 188-95.

Tyagi, G. K., Bhattacharya, S., and Kherdekar, G. (2011) Comfort behaviour of woven bamboo-cotton ring and MJS yarn fabrics. *Indian Journal of Fibre and Textile Research*. 36: 47-52.

Watkins, D. A. and Slater, K. (1981) The moisture vapour permeability of textile fabrics. *Journal of Textile Institute* 72: 11-18.